


Journal Pre-proof

A Comprehensive Review of Hierarchical Porous Carbon Synthesis from Rice Husk

Dinuka Nuwan Tharaka, Nadeeka D. Tissera, Gayan Priyadarshana, Damayanthi Dahanayake

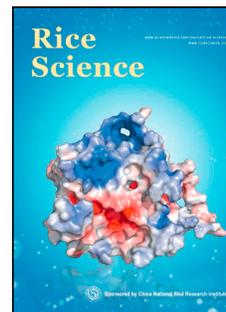

PII: S1672-6308(25)00049-6

DOI: <https://doi.org/10.1016/j.rsci.2025.04.009>

Reference: RSCI 557

To appear in: *Rice Science*

Received Date: 16 January 2025

Accepted Date: 1 April 2025

Please cite this article as: Dinuka Nuwan Tharaka, Nadeeka D. Tissera, Gayan Priyadarshana, Damayanthi Dahanayake, A Comprehensive Review of Hierarchical Porous Carbon Synthesis from Rice Husk, *Rice Science*, <https://doi.org/10.1016/j.rsci.2025.04.009>.

This is a PDF file of an article that has undergone enhancements after acceptance, such as the addition of a cover page and metadata, and formatting for readability, but it is not yet the definitive version of record. This version will undergo additional copyediting, typesetting and review before it is published in its final form, but we are providing this version to give early visibility of the article. Please note that, during the production process, errors may be discovered which could affect the content, and all legal disclaimers that apply to the journal pertain.

Copyright © 2025, China National Rice Research Institute. Hosting by Elsevier B.V.



Review

A Comprehensive Review of Hierarchical Porous Carbon Synthesis from Rice Husk

Dinuka Nuwan THARAKA^{1,2}, Nadeeka D. TISSERA³, Gayan PRIYADARSHANA⁴,
Damayanthi DAHANAYAKE¹

(¹Faculty of Science, NSBM Green University, Mahenwaththa, Pitipana, Homagama 10206, Sri Lanka; ²Faculty of Graduate Studies, Nugegoda 10250, University of Sri Jayewardenepura, Sri Lanka; ³Institute of Technology, University of Moratuwa, Diyagama, Homagama 10200, Sri Lanka; ⁴Faculty of Technology, University of Sri Jayewardenepura, Mahenwaththa, Pitipana, Homagama 10206, Sri Lanka)

Abstract: Hierarchical porous carbon (HPC) materials exhibit superior performance profiles in various applications due to their well-developed multiscale interconnected pore structures. The synthesis of HPC from natural biomass precursors instead of fossil fuel-based precursors has gained considerable attention in recent decades. Rice husk, a globally abundant agricultural waste, offers a sustainable and cost-effective precursor for HPC production. The structural components and inherent silica content of rice husk act as a natural self-template for forming hierarchical pore structures with superior characteristics. In this review, recent studies on preparing rice husk-based HPC are summarized, and synthesis techniques are evaluated. In addition, recent advancements in activation methods and the effect of silica templates are reviewed while comparing these with traditional activated carbon production methods. Potential future directions for research and development activities are also discussed. Rice husk is a highly promising candidate for producing high-performance HPC materials.

Key words: hierarchical porous carbon; rice husk; pyrolysis; rice husk silica template

Hierarchical porous carbon (HPC), a class of porous carbon with interconnected multiscale pores, has attracted much research interest in recent years due to its structural advantages over traditional porous carbon materials (Xiang et al, 2022; Romero et al, 2024). Conventionally, HPCs are fabricated using unsustainable fossil fuel-based precursors. However, the growing demand for eco-friendly and sustainable materials has shifted research toward renewable and low-cost biomass sources as alternative carbon precursors (He et al, 2023). Researchers have prepared HPC and porous carbon materials from different biomass sources with excellent characteristics. Some examples include coconut shells, açai seeds, bagasse, kelp, walnut shells, and

Mikania micrantha (Sun et al, 2019; de Souza et al, 2020; Liu H et al, 2020; Sanni et al, 2020; Mashhadimoslem et al, 2021; Zhao et al, 2023; Zou et al, 2023; Jalalah, et al, 2024a). These materials have various applications in energy storage, water purification, gas adsorption, catalysts, and environmental remediation (Wang et al, 2020; Chakraborty et al, 2022; Jalalah et al, 2023a, 2024b). Although various biomass sources can be utilized to produce HPC, the availability, abundance, and supply need to be considered for sustainable manufacturing because the shortage of raw materials can impact the scalability and feasibility of production. Rice husk has emerged as a highly promising precursor for HPC synthesis due to its natural abundance and

Received: 16 January 2025; **Accepted:** 1 April 2025

Corresponding author: Damayanthi DAHANAYAKE (damayanthi.d@nsbm.ac.lk)

Copyright © 2025, China National Rice Research Institute. Hosting by Elsevier B V

This is an open access article under the CC BY-NC-ND license (<http://creativecommons.org/licenses/by-nc-nd/4.0/>)

Peer review under responsibility of China National Rice Research Institute

<https://doi.org/10.1016/>

unique silica composition.

Rice (*Oryza sativa*) is a staple food for over half the global population, with its demand steadily rising alongside population growth (Bandumula, 2018). According to the Food and Agriculture Organization data, global rice production reaches approximately 769.9 million tons annually, with 510.6 million tons recorded on a milled basis, leading to the generation of millions of tons of rice husks (FAO, 2018). Open burning of rice husks is a common practice in many rice-producing countries, which emits harmful pollutants, greenhouse gases, and fine particulate matter, contributing to significant environmental and health issues (Junpen et al, 2018). Landfilling is another widespread method of rice husk disposal, but rice husks' slow decomposition rate causes them to occupy valuable landfill space for extended periods (Zou and Yang, 2019). These challenges highlight the need for sustainable methods for rice husk waste management. Rice husks have several versatile and high-value applications in porous carbon materials, building materials, silica extraction, adsorbents, and soil amendments (Premaratne et al, 2014; Alam et al, 2020; Kordi et al, 2024).

HPCs derived from biomass are usually produced by pyrolysis-activation techniques (Zhou et al, 2021). However, rice husks are unlike the common lignocellulosic biomasses such as wood or straw, as they contain very high silica levels, typically ranging from 15%–20% by weight (Yerdauletov et al, 2023). Direct pyrolysis and activation of rice husk hardly produce well-developed hierarchical pore structures. Thus, additional processing steps such as silica removal or advanced activation methods are often required to achieve the desired hierarchical structure. The embedded silica nanoparticles in rice husks act as a natural template and play a crucial role in forming hierarchical pore structures (Rybarczyk et al, 2016). The pore size, distribution, and interconnectivity depend heavily on preparation techniques and associated process conditions. Understanding these factors is essential for optimizing HPC properties and enhancing their performance across diverse applications.

Comprehensive reviews have been published on the preparation and synthesis of HPCs from biomass sources (Cuong et al, 2021; Zhou et al, 2021). However, to the best of the authors' knowledge, no review has specifically examined the preparation of HPC from rice husks or the role of silica as a natural template. The

current review focuses on synthesising HPC from rice husks, emphasizing the significance of silica as a natural template. Moreover, various synthesis methods and techniques, including pyrolysis, silica removal methods, chemical and physical activation, are discussed. Finally, the applications and prospects of rice husk-derived HPCs are comprehensively summarized.

Hierarchical porous structure

According to the International Union of Pure and Applied Chemistry, pores are categorized into three types based on their size: micropores (< 2 nm), mesopores (2–50 nm), and macropores (> 50 nm). HPC contains interconnected multi-modal pore structures ranging from micropores to mesopores and macropores, as schematically depicted in Fig. 1-A. Generally, HPCs have a large specific surface area (SSA); however, a high SSA alone does not confirm the presence of a hierarchical porous structure, as sometimes conventional porous/activated carbon exhibits high SSA due to abundant micropores (Xiang et al, 2022; Yan et al, 2023). The defining feature of HPC compared with other porous carbon materials is the interconnectivity of these different pore sizes, forming a hierarchical architecture. Micropores provide a high SSA and numerous adsorption sites, while mesopores act as efficient pathways for ion transport, facilitating rapid diffusion to the interior surfaces where micropores are located (Zhang M X et al, 2021; Zhou et al, 2021). Additionally, macropores act as a reactant reservoir, minimizing diffusion distance and enhancing mass transfer kinetics (Kaur et al, 2019). Interconnected pores across various size ranges contribute synergistically to adsorption capacity, ion transport efficiency, and reactant accessibility, leading to superior performance in energy storage, catalysis, and adsorption applications (Cuong et al, 2021).

Many activated carbon materials have been produced from rice husks using conventional physical and chemical activation techniques without leveraging the natural silica templating effect. Carbon materials prepared by these methods often lack a well-developed hierarchical pore structure or high SSA and predominantly contain one type of pore, typically micropores. These micropores contribute significantly to the adsorption surface area; however, their small size restricts the movement of electrolyte ions, leading to slow diffusion and a sharp decline in capacitance at higher current densities in supercapacitors (Yan et al, 2023). Moreover, not all micropores are readily accessible to ions due to their size and tortuosity, reducing the effective surface area

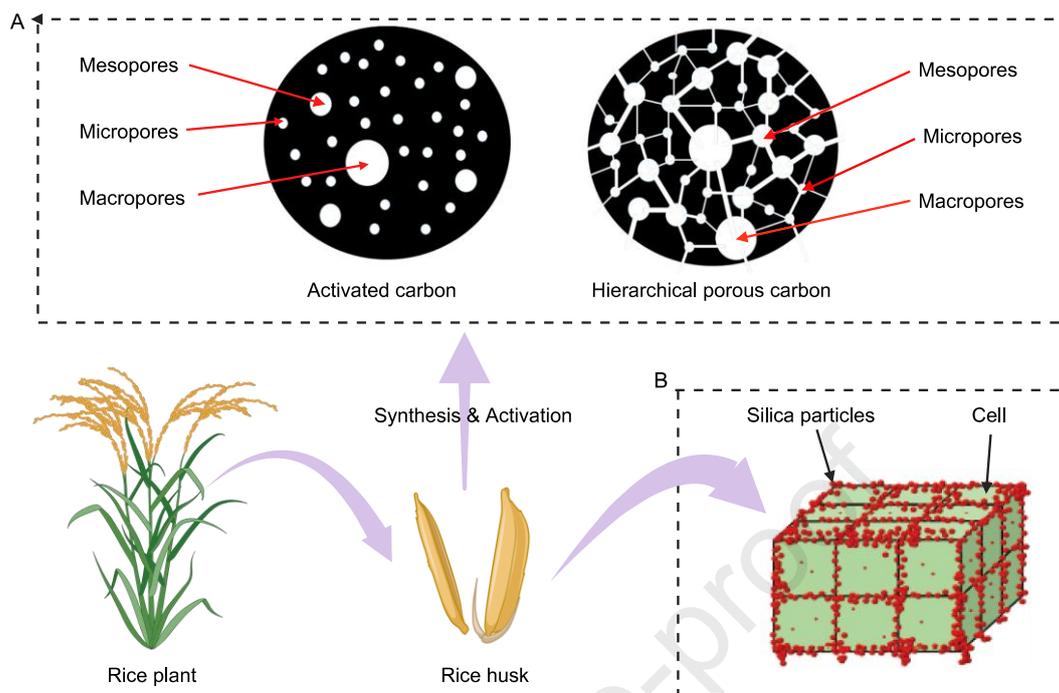


Fig. 1. Structural comparison of activated carbon and hierarchical porous carbon, and silica distribution in rice husk cells.

A, Schematic diagram of hierarchical porous and activated carbon derived from traditional physicochemical activation methods.

B, Schematic representation of silica distribution in rice husk cells.

(Yin et al, 2020; Jiang et al, 2022). This restricts their applicability in advanced applications, and they are usually used as adsorbents. In contrast, rice husk-derived HPC is specifically designed to possess a hierarchical architecture. HPC preparation from rice husk often involves a silica template removal step after carbonization, leveraging the silica content as a natural template (Liu et al, 2015; Cuong et al, 2020).

Components of rice husk

Rice husks serve as the protective outer layer of rice grains, regulating moisture within the grain and preventing excessive water loss that could hinder proper development (Kordi et al, 2024). Rice husk consists of three main layers: the epidermis (the outermost layer, often featuring macro-hairs on its surface), the subhypodermis, and the hypodermis (Chen et al, 2018). Rice husk possesses vascular bundles that form natural microporous channels varying in size between 2 and 10 μm (Liu et al, 2015). These channels facilitate the transport of water and essential nutrients required for rice growth. The chemical composition of rice husk varies depending on the rice variety, growing region, and cultivation conditions (Alam et al, 2020). It primarily consists of cellulose (35%–40%), hemicellulose (15%–20%), lignin (20%–25%), and silica (15%–25%) (Gao et al, 2018;

Yerdauletov et al, 2023). Cellulose, the main structural component, is a complex poly-saccharide primarily composed of glucose monomers connected through β -1,4-glycosidic linkages. Hemicellulose is another carbohydrate component present in plant cell walls. Lignin, a complex organic polymer, enhances the strength and rigidity of plant tissues.

The primary inorganic component in rice husks is silica, which exhibits in an amorphous form. Rice roots absorb silica as silicic acid, which is transported to the outer epidermal walls and transformed into silica (Yamaji and Ma, 2009). Analysis using scanning electron microscopy and energy-dispersive X-ray spectroscopy revealed that silica is unevenly distributed within rice husks, with the highest concentration found on the outer layer, forming a protective coating (Chen Z M et al, 2020). Fig. 1-B shows a schematic diagram of silica distribution inside the rice husk. A significant fraction of silica particles ranges from 1 to 7 nm in size, while a smaller fraction consists of larger particles, ranging from 8 to 22 nm (Larichev et al, 2015). Silica forms a 3D nanostructured skeleton within the rice husk, acting as a natural template alongside organic components. Silica and organic components in rice husks mutually serve as structural templates (Chen Z M et al, 2020).

Preparation of HPC

HPC can be synthesized through various methods (Dutta et al, 2014; Kaur et al, 2019; Xiang et al, 2022; Yan et al, 2023), including template-based and template-free approaches. Template techniques are divided into hard-template and soft-template methods. Hard-template methods involve impregnating rigid templates (e.g. silica or metal oxides) with a carbon precursor. After carbonization, the template is removed via acid etching, leaving a carbon material with pores replicating the template's structure. The soft-template method employs self-assembling surfactants or block copolymers as templates to direct the organization of the carbon precursor. The dual-template approach integrates both hard and soft templates to create a well-defined, multi-scale pore structure. Template-free methods include pyrolysis activation, chemical vapor deposition, and other emerging techniques. Most biomass inherently contains naturally organized structures ranging from molecular to tissue levels. Pyrolysis, followed by activation, effectively utilizes these natural features to

produce HPC, making it an attractive and sustainable approach for waste biomass conversion (Zhou et al, 2021).

Preparation of HPC from rice husk

Recent studies on preparing rice husk-based HPC are summarized in Table 1. The process generally involves carbonization of rice husk, removal of silica templates, and activation. The hierarchical porosity achieved depends on factors such as activation temperature, duration, and the rice husk precursor variety. There is a lack of comprehensive studies comparing the influence of rice husk variety, composition, and cultivation practices on the structural and functional characteristics of the synthesized HPC. To the best of the authors' knowledge, no study has specifically identified the optimal rice husk type for HPC production. Further research is needed to analyze how these rice husk compositional variations influence HPC synthesis.

The hierarchical porous structure of rice husk-derived

Table 1. Preparation methods of rice husk-based hierarchical porous carbon.

Carbonization process	Silica removal	Activation process	Impregnation ratio	SSA (m ² /g)	PV (cm ³ /g)	Mesoporosity (%)	Reference
Pyrolysis at 800 °C for 1 h under N ₂ atmosphere	HF leached	Steam activation at 900 °C for 3 h	–	1 340	1.20	–	Tabata et al, 2010
Pyrolyzed at 500 °C for 3 h under N ₂ atmosphere	HF leached	KOH activation at 800 °C for 2 h	4:1	1 094	0.61	42.6	Wang et al, 2014
Pyrolysis at 500 °C for 1 h under N ₂ atmosphere	NaOH leached	KOH activation at 700 °C for 1 h	4:1	2 804	1.79	–	Liu et al, 2015
Hydrothermal carbonization	NH ₄ HF ₂ leached	Higher pyrolysis	–	525	0.48	76.4	Rybarczyk et al, 2016
Pyrolysis at 500 °C for 1 h under N ₂ atmosphere	NaOH leached	KOH activation at 700 °C for 2 h	4:1	1 751	1.11	55.9	Yuan et al, 2016
Pyrolyzed under an Argon atmosphere	HF leached	Higher pyrolysis	–	533	0.39	–	Fang et al, 2017
Pyrolysis at 700 °C for 3 h under N ₂ atmosphere	HF leached	KOH activation at 700 °C for 3 h	3:1	2 242	1.33	–	Xiao et al, 2017
Pyrolysis at 500 °C for 1 h under N ₂ atmosphere	Base leached	NaOH/KOH co-activation at 800 °C for 1 h	3:1	2 747	1.40	–	Wang C et al, 2018
Pyrolyzed at 500 °C for 1 h under N ₂ atmosphere	NaOH leached	KOH/CO ₂ physicochemical activation	3:1	2 330	1.32	81.0	Cuong et al, 2019
Pyrolysis at 900 °C for 1 h under N ₂ atmosphere	HF leached	Steam activation at 850 °C	–	268	0.23	–	Kim et al, 2019
Pyrolysis at 450 °C for 3 h under N ₂ atmosphere	–	KOH activation at 750 °C for 1 h	3:1	1 320	0.65	30.7	Shen et al, 2019
Pyrolysis at 600 °C for 1 h under N ₂ atmosphere	NaOH leached	CuCl ₂ activation at 800 °C	10:1	1 339	0.80	33.7	Tian et al, 2019
Pyrolysis at 600 °C for 1 h under N ₂ atmosphere	NaOH leached	NaOH activation at 750 °C for 1 h	2.5:1	1 789	1.15	37.4	Chen Z M et al, 2020
Pyrolyzed at 800 °C for 2 h under N ₂ atmosphere	NaOH leached	KOH activation at 800 °C	2:1	1 839	1.21	58.0	Cuong et al, 2020
Pyrolysis	NaOH leached	Higher pyrolysis	–	242	0.15	–	Nie et al, 2020
Hydrothermal carbonization	NaOH leached	–	–	445	–	–	Hou et al, 2021
Pyrolysis	Na ₂ CO ₃ leached	NaOH activation at 800 °C	3:1	2 686	1.62	64.0	Zhang S P et al, 2021
Pyrolysis at 1000 °C for 2 h under N ₂ atmosphere	NaOH leached	–	–	643	0.52	–	Qin et al, 2023

SSA, Specific surface area; PV, Total pore volume; Mesoporosity (%), Ratio of mesopore volume to PV. Impregnation ratio refers to the mass ratio of activating agents to rice husk. HF, Hydrofluoric acid. '–' indicates data not mentioned in the original paper.

HPC emerges through a sequence of structural transformations during carbonization, silica removal, and activation. Liu et al (2015) proposed a mechanism of hierarchical pore formation from rice husks. During carbonization, organic components in the rice husk decompose, releasing volatile matter, and leaving behind a carbon-silica composite. This stable porous structure preserves the vascular bundles of the rice husk. The composite initially has a small surface area. Base leaching removes the nano-silica, resulting in a templated carbon characterized by a 3D surface structure and parallel internal vascular channels. Chemical activation then gradually transforms this templated carbon into a hierarchical porous structure. At the start of activation, activators accumulate in the porous channels of the nano-structured carbon via capillary interaction. As activation proceeds, these channels widen into macropores and micropores, followed by the development of mesopores within them. Eventually, these pores become interconnected, forming a hierarchical porous framework.

The optimal HPC production method depends on the target application, cost, performance, and environmental impact. Overall, the most common approach combines pyrolysis, NaOH leaching for silica removal, and KOH/NaOH activation, which yields well-developed hierarchical porosity and superior performance.

Carbonization

Carbonization is a process that involves the thermal decomposition of carbonaceous materials by heating under oxygen-depleted conditions. Generally, carbonization can be conducted through pyrolysis or hydrothermal carbonization. Optimizing carbonization parameters is important because this process significantly affects the properties of the resulting carbon materials.

Pyrolysis of rice husk

Pyrolysis of rice husks is the most widely used carbonization method for producing HPC due to its simplicity and scalability. The process involves heating rice husks in an inert environment (nitrogen or argon, N₂/Ar) and yields three main products: biochar, a solid carbon-rich material; bio-oil; and non-condensable gases (e.g., methane, hydrogen, carbon monoxide, and carbon dioxide) (Asadi et al, 2021). Jia et al (2020) studied rice husk pyrolysis characteristics using thermogravimetric analysis and identified four stages: Drying stage (20 °C–110 °C) releases moisture and breaks hydrogen bonds in macromolecular structures,

causing approximately 10% mass loss. Preheating transition stage (110 °C–220 °C) involves hemicellulose depolymerization and recombination, resulting in a further mass loss of around 3%. Main pyrolysis stage (220 °C–600 °C) involves significant thermal decomposition of rice husk, breaking carbohydrate chains into simpler. Carbonization stage (above 600 °C) decomposes the remaining lignin slowly, resulting in a gradual mass loss. At temperatures above 750 °C, silica facilitate carbon graphitization (Yerdauletov et al, 2023). Above 900 °C, silica crystallinity increases, evidenced by sharper X-ray diffraction peaks (Barakat et al, 2024). Pyrolysis primarily forms micropores in rice husk-derived porous carbons, and the resulting carbon-silica composite exhibits a low surface area.

Hydrothermal carbonization (HTC)

HTC involves heating biomass in water (180 °C–250 °C) under pressure for several hours (Bushra and Remya, 2024). This energy-efficient method can process rice husks without pre-drying. During HTC, rice husks undergo dehydration, decarboxylation, and polymerization (Kaur et al, 2019), yielding hydrochar rich in oxygen-containing functional groups (Nizamuddin et al, 2018).

Silica template removal

Silica removal is typically achieved through chemical etching; the most used agents include hydrofluoric acid (HF) and sodium hydroxide (NaOH). HF effectively removes silica at room temperature (Tabata et al, 2010). Xiao et al (2017) reported near-zero silicon content after 25% HF treatment (confirmed by X-ray photoelectron spectroscopy). However, HF is toxic, corrosive, expensive, and requires hazardous waste management (Sevilla et al, 2021). NaOH reacts with silica to form soluble sodium silicate (Na₂SiO₃) (Alam et al, 2020). Xue et al (2019) found that 5% NaOH at room temperature removes surface silica, but higher concentrations or elevated temperatures are needed for complete removal. Compared with HF leaching, NaOH treatment is less efficient and energy-intensive at high temperatures.

Ammonium bifluoride (NH₄HF₂) and sodium carbonate (Na₂CO₃) have been investigated as alternative agents for silica removal. NH₄HF₂ dissociates to release HF *in situ*, reducing direct HF handling but still hazards (Rybarczyk et al, 2016). Na₂CO₃ is less corrosive, posing fewer environmental hazards than HF and NaOH (Sevilla et al, 2021), which achieves desilication at 90 °C (Zhang S P et al, 2021), though energy-intensive.

Effect of silica removal

Silica removal increases SSA and pore volume (Chen W et al, 2020). A study reported that a carbon-silica composite, before silica removal, exhibited an SSA of approximately 30.26 m²/g along with a pore volume of 0.05 cm³/g (Qin et al, 2023). After silica removal, the SSA increased to values exceeding 159.65 m²/g, while the pore volume significantly improved to around 0.24 cm³/g. Another study reported that before desilication, the mesopore volume reached 0.03 cm³/g, representing 24.62% of the overall pore volume, and after silica removal, the mesopore volume rose to 0.14 cm³/g, constituting 59.31% of the total pore volume (Zhang S P et al, 2021). These enhancements are due to the size of silica nanoparticles within rice husk closely matching the diameters of mesopores and macropores (Park et al, 2003). Upon removal, it promotes the development of pores, particularly mesopores, leading to a hierarchical structure (Rybarczyk et al, 2016). Rice husk-derived HPCs, following the removal of the silica template, display a marked improvement in supercapacitor performance, achieving a maximum specific capacitance of 429 F/g at 0.5 A/g, along with excellent rate (Xiao et al, 2017). In comparison, HPCs without silica removal exhibit a significantly lower specific capacitance of 364 F/g at 0.5 A/g and poor rate capability. This enhancement is primarily due to the enhanced porous structure resulting from silica removal, which increases the available surface area for charge storage and enhances ion transport efficiency within the electrode material. Silica removal also alters the morphology of rice husk char. While the char retains the vascular bundle and ridge-like structure of the original rice husk, its surface becomes rougher due to the newly exposed pores (Rybarczyk et al, 2016).

Silica can react with some activating reagents, like NaOH and KOH, which can reduce the efficiency of the activation process (Wang Z F et al, 2018; Zhang S P et al, 2021). Liu et al (2019) investigated how silica influences the activation process, comparing rice husk samples, RHC1 (rice husk without silica removal) and RHC2 (rice husk with silica removal via NaOH leaching). Results showed that in RHC1, silica reacts preferentially with KOH, forming potassium silicate. The potassium silicate forms a 'shell' around the carbon, hindering KOH from reacting with it. This hinders the enlargement of pores in the carbon. This process leads to many micropores being formed instead of mesopores. As a result, the activated carbon obtained through this method exhibits a high SSA of 3 263 m²/g,





resulting in a low mesopore ratio (36.1%). This produces a high specific capacitance of 315 F/g and a high energy density. However, the low mesopore ratio leads to poor rate capability. Conversely, in RHC2, removing the silica from the rice husk before activation generates initial pores within the material. During the activation process, these pores enlarge into mesopores. The carbon material obtained through this process has a high mesopore ratio (73.5%), results in excellent rate performance, maintaining 77% capacitance retention as the current density rises from 0.5 to 20 A/g.

Activation of rice husk

Rice husk char can be activated through chemical, physical, and physiochemical methods. Activation temperatures, agents, time, and process parameters can vary depending on the technique.

Physical activation




Physical activation involves treating rice husk with oxidizing gases, such as CO₂ or steam, at high temperatures. The gases react with the carbon atoms in the rice husk char structure; new pores are formed as carbon atoms are removed. Simultaneously, pores formed during the carbonization stage are widened (Menya et al, 2018; Yin et al, 2020). The main chemical reactions involved are:



Physical activation of rice husk char with CO₂ under different temperature conditions revealed that weight loss rises with higher activation temperatures, primarily due to carbon loss (Wazir et al, 2024). Physical activation is generally considered a greener option than chemical activation because it avoids using harsh and potentially hazardous chemicals. The main byproducts are gases that can be managed more easily than the wastewater generated during chemical activation. However, there are some drawbacks to consider. Compared with chemical activation, physically activated carbon often has a lower SSA. This can limit its effectiveness in applications where high adsorption capacity is essential; it also requires elevated temperatures, contributing to significant energy consumption, thereby increasing operational costs and offering less control over pore size distribution than chemical activation. This can be a disadvantage for applications that require specific pore characteristics for optimal performance.

Chemical activation

Chemical activation is a widely used method to produce porous carbon, employing chemical reagents as activating agents. This involves impregnating rice husks with chemical agents and heat treatment in an inert atmosphere. Commonly used reagents for chemical activation of rice husk are KOH, NaOH, ZnCl₂, H₃PO₄, and CuCl₂. Compared with other chemical agents, KOH is renowned for its superior performance as it generally requires lower temperatures, produces higher biochar yield, and can result in high SSA porous carbon, reaching up to 3 000 m²/g (Chen W et al, 2020). The KOH activation mechanism involves complex chemical reactions (Yin et al, 2020). The major reactions involved are:





KOH reacts with carbon in the rice husk to form K₂CO₃, metallic potassium, hydrogen gas, and carbon monoxide. Gaseous intermediates generated, such as CO₂, H₂O, and H₂, escape from the biochar structure, creating a network of pores. CO₂ and H₂O also serve as activating agents during physical activation, further enhancing pore development. Metallic potassium can intercalate into the carbon lattice, expanding the structure and creating micropores (Xiang et al, 2022).

Several key factors, including the impregnation ratio, activation temperature, and activation time, influence the activation process for preparing HPC. Cuong et al (2020) prepared HPC from rice husk using a KOH impregnation ratio of 2:1 (KOH:rice husk) and an activation temperature of 800 °C, demonstrating significant variations in structural properties based on activation time. When the activation time was extended from 0.5 to 2 h, the SSA of the HPC materials increased significantly from 1 520 to 1 839 m²/g. However, further increasing the activation time to 3 h resulted in the SSA and pore volume reducing to 1 702 m²/g and 1.14 cm³/g, respectively. This decrease was attributed to the collapse of micropores, likely due to prolonged exposure to harsh activating conditions. A study reported that higher impregnation ratios, such as 3:1, enhance SSA and mesoporosity, with SSA increasing from 1 734 m²/g at 2:1 to 2 330 m²/g at 3:1 under identical conditions (Cuong et al, 2019). However, excessive ratios lead to pore collapse due to overreaction with carbon, reducing mesoporosity. Similarly, higher activation temperatures improve porosity and mesopore development,

as seen with an increase in mesopore-to-total surface area ranging from 0.23 at 600 °C to 0.73 at 800 °C. Excessive temperatures, however, weaken the carbon framework, causing structural collapse. These findings highlight the need to optimize both parameters to balance porosity and structural integrity.

NaOH is another commonly used activating agent. The reactions involved during activation can be represented by the following equations (Heidarinejad et al, 2020):



Sodium can intercalate into the carbon structure, expanding the spaces between carbon atoms and contributing to pore development. Additionally, gases like CO, CO₂, and H₂ are released when NaOH reacts with carbon materials, creating pores within the carbon structure. However, variations in activation mechanisms result in porous carbons with lower surface areas when produced via NaOH activation compared with KOH activation.

Unlike traditional activators such as KOH and NaOH, CuCl₂ minimizes reactor corrosion and achieves an 80% recovery rate, enhancing sustainability (Tian et al, 2019). However, CuCl₂-activated porous carbon exhibits lower surface areas than KOH- and NaOH-activated HPC.

Physicochemical activation combines chemical and physical activation agents. According to Table 1, physicochemical activation achieves good performance metrics, including a high SSA of 2 330 m²/g and significant mesoporosity, with a mesopore ratio of 81%. While physicochemical activation offers these advanced characteristics, it is more complex than single activation methods, and greater investment is needed for equipment and reagents.

Other methods for preparation of rice husk-derived HPC

Liang et al (2017) developed a method for synthesizing HPC from rice husk that eliminates both activation and post-treatment steps by combining rice husk with polytetrafluoroethylene (PTFE) powder and carbonizing the mixture. During carbonization, PTFE decomposes and releases HF, which *in situ* etches away the silica present in rice husks. This single-route carbonization and silica removal process is environmentally friendly and cost-effective since it eliminates the need for additional steps and hazardous chemicals like HF. The

resulting HPCs exhibit high SSA, reaching up to 2 051 m²/g and a high specific capacitance of 317 F/g at a current density of 50 A/g. N₂ adsorption-desorption isotherms confirmed the existence of a hierarchical pore structure consisting of micropores, mesopores, and macropores. Future research could investigate the scalability of this process for industrial applications.

Peng et al (2019) proposed an innovative strategy to fabricate HPC using mixed biomass wastes, specifically crab shells and rice husks, as raw materials. In this method, a mixture of crab shells and rice husks was hydrothermally carbonized, and HCl was used to soak and remove CaCO₃, followed by KOH. The resultant HPCs showed a unique 3D interconnected pore architecture with a large surface area of 3 557 m²/g, facilitating electrolyte ion transport and offering abundant energy storage capacity. Additionally, the HPCs exhibit a high specific capacitance of 474 F/g and excellent cyclic stability, retaining 95.6% of their capacitance over 20 000 charge/discharge cycles while employing 6 mol/L KOH as the electrolyte.

Molten salt carbonization is a one-step process that converts biomass into functional biochar using molten salt, which acts as a pyrolysis medium and a chemical activating agent for the biomass (Egun et al, 2022). This allows for carbonization and activation to occur simultaneously, streamlining the production of functional biochar. Liu et al (2023) reported the production of HPC from rice husk via a single-step Na₂CO₃ and K₂CO₃ molten carbonization process. The salt bath acts as a chemical activating reagent, and the alkaline melt also dissolves the silica templates within the rice husks, eliminating the need for additional steps for silica template removal. The resultant HPC has a SSA of 1012.8 m²/g and a hierarchically porous structure, as demonstrated by isotherms and pore size distribution curves. Using eutectic mixtures of multiple salts can lower the melting point compared with single-component salts, and the pore properties of carbon materials can be tuned by altering the composition and ratios of the composite salts in the molten mixture (Yan et al, 2023). However, the corrosive nature of molten salts, especially at high temperatures, can challenge reactor materials and equipment. Selecting appropriate corrosion-resistant materials for reactors and handling systems is essential to ensure process longevity and safety.

Cheng et al (2020) fabricated HPC by pre-treating rice husks with cellulose-degrading fungus. This treatment enhances carbonization and chemical activation efficiency by breaking down the rice husks' internal and external

microstructures while altering the lignin, cellulose, and hemicellulose composition. The resulting HPC material exhibits an SSA of 3 714 m²/g and a hierarchical micro-mesoporous structure. It demonstrated remarkable adsorption properties, including a high toluene adsorption capacity of 708 mg/g at 100 mg/kg, outperforming porous carbons derived from untreated rice husks (538 mg/g).

Using a novel two-step KOH activation method, Li et al (2024) prepared HPC from rice husks. The process involved carbonization of rice husk to biochar, followed by a pre-activation step at 400 °C under nitrogen flow and a final activation at 800 °C. The sample produced through this method was labelled RHAC-Tpre400-K3. For comparison, a control sample was prepared using a conventional single-step KOH activation method and labelled RHAC-K3. Compared with traditional single-step KOH activation, the optimized method (RHAC-Tpre400-K3) achieves a well-developed 3D hierarchical porous structure with superior specific capacitance performance relative to RHAC-K3. In pre-activation, additional activation sites are created by KOH reactions. These sites expand during the subsequent 800 °C activation, facilitating the formation of interconnected pores. Heteroatom doping involves incorporating elements other than carbon into the HPC structure, which can alter its physicochemical and electronic characteristics, enhancing its applicability across various applications. Xue et al (2020) prepared nitrogen-doped rice husk-derived HPC by the pyrolysis of urea-impregnated rice husk and then leaching out the silica template using HF. The resulting materials display a high gravimetric capacitance of 242 F/g and volumetric capacitance of 306 F/cm³ at 0.5 A/g in 1 mol/L H₂SO₄ electrolyte, surpassing the performance of activated carbon synthesized via KOH or ZnCl₂ activation.

Comparison with traditional method

Recent studies on preparing porous carbon/activated carbon from traditional physical and chemical activation are summarized in Table 2. Although traditional chemical activation can achieve high surface area and pore distribution, porous carbon lacks hierarchical architecture. The general procedure for preparing porous carbon/activated carbon typically includes pyrolysis and/or activation of rice husk. Sometimes, acidic or basic pretreatments are employed to reduce the metallic impurities and ash content in rice husks (Barakat et al, 2024).

Applications of rice husk-derived HPC

Table 2. Recent studies on preparation of activated carbon through traditional methods using rice husk.

Pre-treatment	Carbonization process	Activation process	Impregnation ratio	SSA (m ² /g)	PV (cm ³ /g)	Reference
Base leached	406 °C for 1 h under N ₂ atmosphere	Steam	–	1 016	0.58	Menya et al, 2018
Not leached	Pyrolyzed at 400 °C	KOH	1:3	887	0.48	Liu Z Y et al, 2020
Not leached	Pyrolyzed at 500 °C for 3 h under N ₂ atmosphere	KOH	1:3	2 087	0.99	Lv et al, 2020
Not leached	Pyrolyzed at 400 °C for 4 h under N ₂ atmosphere	NaOH	1:4	429	0.29	Saad et al, 2020
Not leached	Pyrolyzed at 500 °C for 1 h under N ₂ atmosphere	KOH	1:2	890	0.44	He et al, 2021
Not leached	Pyrolyzed at 450 °C under N ₂ atmosphere	NaOH	1:3	2 755	1.54	Silva et al, 2021
Not leached	Pyrolyzed at 600 °C for 2 h	KOH	1:3	755	0.39	Nandi et al, 2023
Not leached	Pyrolyzed at 750 °C N ₂ atmosphere	KOH	1:4	3 050	1.10	Yerdauletov et al, 2023
Not leached	Pyrolyzed at 400 °C under N ₂ atmosphere	CO ₂	–	502	0.12	Lesbayev et al, 2024
Not leached	Pyrolyzed at 900 °C for 1 h under N ₂ atmosphere	CO ₂	–	502	0.12	Wazir et al, 2024

SSA, Specific surface area; PV, Total pore volume. Impregnation ratio refers to the mass ratio of activating agents to rice husk. ‘–’ indicates data not mentioned in the original paper.

Rice husk-derived HPCs perform better in diverse applications due to their high SSA, interconnected porous structure, and unique physicochemical properties. The most prominent area of rice husk-derived HPC application is energy storage, specifically supercapacitors. The supercapacitor functionality of HPC from rice husk depends on electrical double-layer capacitance (EDLC) and pseudo-capacitance mechanisms (Zhou et al, 2021). In EDLC, the charge is stored through the electrostatic adsorption and desorption of ions at the electrode-electrolyte interface, thus creating an electric double layer without any faradaic reaction (Tian et al, 2019; Zhang S P et al, 2021). Their high SSA provides abundant sites for electrolyte ion accumulation, leading to high capacitance, and an interconnected network of pores facilitates rapid ion transport, enhancing rate capability and power density (Liu et al, 2015; Liang et al, 2017; Wang Z F et al, 2018). Oxygen-containing groups, such as hydroxyl, carboxyl, and carbonyl, are commonly

found in HPCs and can enhance wettability, promoting electrolyte accessibility to the pore structure (Liu et al, 2015). Pseudo-capacitance arises from fast redox reactions at electroactive sites. Integrating metal oxides into HPC surfaces can enhance pseudo-capacitance through additional reversible redox reactions (Yuan et al, 2016). Nitrogen doping can introduce functional groups like pyridinic and quaternary nitrogen, enhancing electrical conductivity and contributing to pseudo-capacitance (Xue et al, 2020). The capacitance performances of rice husk-derived HPC and other biomass-derived HPCs are shown in Table 3. Rice husk-derived HPC has similar and sometimes higher performance than other biomass-derived HPCs.

Rice husk-derived HPC has been studied as an electrode material for lithium-ion, sodium-ion, and lithium-sulfur batteries. In lithium-ion batteries, the porous structure can provide a large SSA and accommodate the volume changes during lithium insertion and

Table 3. Electrochemical performance of rice husk-derived hierarchical porous carbon (HPC) and other biomass-derived HPCs in supercapacitor applications.

Biomass	Activation	SSA (m ² /g)	Test system/ Electrolyte	Current density (A/g)	Specific capacitance (F/g)	Reference
Rice husk	KOH	2 804	6 mol/L KOH, Two-Electrode	0.5	278	Liu et al, 2015
Rice husk	PTFE	2 051	6 mol/L KOH, Two-Electrode	10	245	Liang et al, 2017
Rice husk	KOH	2 242	6 mol/L KOH, Two-Electrode	0.5	429	Xiao et al, 2017
Rice husk	NaOH-KOH	2 747	1 mol/L H ₂ SO ₄ , Two-Electrode	0.5	194.6	Wang C et al, 2018
Withered rose	KOH/KNO ₃	1 911	6 mol/L KOH, Three-Electrode	0.5	208	Zhao et al, 2018
Rice husk	CuCl ₂	1 339.9	6 mol/L KOH	0.5	165.2	Tian et al, 2019
Acai seed	KOH	3 846	1 mol/L KOH, Three-Electrode	1.0	346	de Souza et al, 2020
Rice husk	KOH	1 839	1 mol/L NaCl, Three-Electrode	0.1	120.5	Cuong et al, 2020
Olive wood	KOH	1 352	1 mol/L H ₂ SO ₄ , Two-Electrode	0.125	231	Elmouwahidi et al, 2020
Hibiscus sabdariffa fruits	KOH	1 720.5	2 mol/L KOH, Three-Electrode	0.5	194.5	Hamouda et al, 2021
Rice husk	NaOH	1 789	6 mol/L KOH, Two-Electrode	0.5	256	Hou et al, 2021
Foxtail grass seeds (N and S co-doped)	NaHCO ₃ /KHCO ₃	819	6 mol/L KOH	0.5	358	Liang et al, 2021
Bagasse	KOH	3 135	6 mol/L KOH, Two-Electrode	0.5	410.5	Tan et al, 2021
Rice husk	NaOH-KOH	3 046	6 mol/L KOH, Two-Electrode	0.2	312	Zhang S P et al, 2021
Enhydra fluctuant leaves	KOH	1 082	1 mol/L H ₂ SO ₄ , Three-Electrode	1.0	428	Jalalah et al, 2023b
Coconut shell	KOH	2 143.6	6 mol/L KOH, Three-Electrode	0.5	317	Zhao Y et al, 2023
Turmeric leaves	NH ₄ Cl/KOH	541	0.5 mol/L H ₂ SO ₄ , Three-Electrode	1.0	389	Chakraborty et al, 2024

extraction, leading to high specific capacity and stable cycle performance (Hou et al, 2021). Similarly, in sodium-ion batteries, HPC demonstrates a low charge/discharge voltage platform and high SSA, promoting efficient sodium-ion diffusion and improved electrochemical stability (Nie et al, 2020). In lithium-sulfur batteries, HPC's interconnected mesoporous and microporous network functions as a conductive scaffold for sulfur loading, enabling better sulfur utilization and mitigating polysulfide shuttling (Rybarczyk et al, 2016).

Rice husk-derived HPC is a promising material for water purification and environmental remediation, particularly in the adsorption of heavy metals and organic compounds and capacitive deionization (CDI). HPCs' high surface area and functional groups facilitate the efficient adsorption of heavy metal ions from aqueous solutions. Cuong et al (2019) reported an HPC material exhibiting an SSA of 2 330 m²/g and an 81% mesopore-to-total surface area ratio, with an adsorption capacity of 265 mg/g and efficient adsorption kinetics for copper ions. CDI is a process that uses a pair of electrodes with opposite charges to generate an electrostatic double layer, which captures and removes ions from water (Kim et al, 2019; Siriwardane et al, 2021). In CDI, researchers have reported that rice husk-derived HPC-based electrodes can remove inorganic ions such as NH⁴⁺, Mg²⁺, and Cu²⁺, exhibiting high electro-sorption capacities and requiring low energy for water desalination (Cuong et al, 2020).

Tabata et al (2010) studied rice husk-derived HPC for *in vivo* applications. Rats with pneumonia-induced renal failure were fed 5% HPC for 3 d. The rats' plasma analysis revealed a remarkable decrease in uremic toxins after HPC administration. It demonstrated greater effectiveness in decreasing uric acid levels than activated carbon, a commonly used adsorbent. The study also concluded that HPC has low toxicity, as demonstrated by a separate study on normal rats. The rats showed no significant weight changes after consuming feed containing 5% HPC for 2 weeks.

The structural adaptability and physicochemical properties of husk-derived HPC also make them suitable for electromagnetic wave absorption applications (Fang et al, 2017). These materials exhibit excellent absorption performance, positioning them as promising candidates for electromagnetic shielding in electronics and communication devices.

Future perspectives and potential applications

Researchers have explored HPC from biomass sources other than rice husk for gas sensors, photocatalysis, and advanced biomedical applications (Sun et al, 2016; Zhou et al, 2021). Although such applications have not been extensively studied for rice husk-derived HPC, its hierarchical porosity, surface functionalization potential, and stability make it an excellent candidate for emerging applications. In addition, hybrid structures combining rice husk-derived HPC with nanomaterials can enhance overall material performance. HPC-based polymer composites may improve mechanical strength and chemical resistance, enabling their use in membranes, coatings, and hydrogen storage applications. Functionalized rice husk-based-HPC can also support CO₂ capture and conversion. While significant progress has been made, synthesizing HPC from rice husk presents opportunities for scientific and technological advancements. Future research on synthesizing HPC from rice husk should prioritize addressing current gaps and expanding its applications. A major focus area is replacing hazardous chemicals like HF in silica removal processes with safer and greener alternatives, such as sodium carbonate. This is the bottleneck of many HPC preparation studies because hazardous chemicals can cause environmental damage. Further detailed studies on activation conditions, such as temperature, time, and activating agents, are necessary to better control pore size distribution and surface area. Innovations in physicochemical activation and hybrid approaches, including green activation methods like biological methods, should be explored to enhance the efficiency of HPC production. Many studies are limited to laboratory-scale experiments; therefore, pilot-scale and industrial-scale investigations are essential to evaluate the feasibility of rice husk-derived HPC production. Developing cost-effective and energy-efficient systems for large-scale synthesis is critical for commercialization. Rice husk-derived HPC has primarily been researched for energy storage applications and should be explored in a broader range of applications, such as catalysts and dye molecule adsorption. Carbon-based materials have been successfully incorporated to enhance textile properties (Gunasekera et al, 2015). Future research could focus on integrating HPC into textile materials for advanced multifunctional applications. Combining HPC production with other rice husk utilization pathways, such as silica extraction, can enhance resource efficiency and sustainability. By addressing these research directions, the synthesis of HPC from rice husk can advance toward achieving sustainable and high-performance material solutions

for a wide range of global challenges.

Conclusion

Rice husk is a good candidate for the synthesis of HPC because of its low-cost availability and sustainability. The unique self-templating effect of silica in rice husk facilitates the formation of hierarchical porosity with a high SSA, well-interconnected pores, and tunable physicochemical characteristics suitable for the desired application. The general method of HPC preparation involves carbonization, silica removal, and subsequent physical or chemical activation. However, its commercialization faces several challenges, such as the environmental impact of silica removal, optimizing synthesis conditions, scalability, and significant energy consumption in synthesis processes. Novel emerging approaches have shown promise to address these challenges. With continued advancements in synthesis and functionalization innovations, rice husk-derived HPC could provide a sustainable and high-performance alternative to fossil fuel-derived carbons, addressing critical global challenges in the energy and environmental sectors.

REFERENCES

- Alam M M, Hossain M A, Hossain M D, et al. 2020. The potentiality of rice husk-derived activated carbon: From synthesis to application. *Processes*, **8**(2): 203.
- Asadi H, Ghorbani M, Rezaei-Rashti M, et al. 2021. Application of rice husk biochar for achieving sustainable agriculture and environment. *Rice Sci*, **28**(4): 325-343.
- Bandumula N. 2018. Rice production in Asia: Key to global food security. *Proc Natl Acad Sci Ind Sect B Biol Sci*, **88**(4): 1323-1328.
- Barakat N A M, Mahmoud M S, Moustafa H M. 2024. Comparing specific capacitance in rice husk-derived activated carbon through phosphoric acid and potassium hydroxide activation order variations. *Sci Rep*, **14**(1): 1460.
- Bushra B, Remya N. 2024. Biochar from pyrolysis of rice husk biomass: Characteristics, modification and environmental application. *Biomass Convers Biorefin*, **14**(5): 5759-5770.
- Chakraborty R, Vilya K, Pradhan M, et al. 2022. Recent advancement of biomass-derived porous carbon based materials for energy and environmental remediation applications. *J Mater Chem A*, **10**(13): 6965-7005.
- Chakraborty R, Sharma A, Maji P K, et al. 2024. Nitrogen and oxygen self-doped hierarchical porous carbon nanosheets derived from turmeric leaves for high-performance supercapacitor. *Inorg Chim Acta*, **567**: 122056.
- Chen W, Gong M, Li K X, et al. 2020. Insight into KOH activation mechanism during biomass pyrolysis: Chemical reactions between O-containing groups and KOH. *Appl Energy*, **278**: 115730.
- Chen Z M, Wang X F, Xue B C, et al. 2020. Rice husk-based hierarchical porous carbon for high performance supercapacitors: The structure-performance relationship. *Carbon*, **161**: 432-444.
- Chen Z Y, Xu Y Z, Shivkumar S. 2018. Microstructure and tensile properties of various varieties of rice husk. *J Sci Food Agric*, **98**(3): 1061-1070.
- Cheng H R, Sun Y H, Wang X H, et al. 2020. Hierarchical porous carbon fabricated from cellulose-degrading fungus modified rice husks: Ultrahigh surface area and impressive improvement in toluene adsorption. *J Hazard Mater*, **392**: 122298.
- Cuong D V, Liu N L, Nguyen V A, et al. 2019. Meso/micropore-controlled hierarchical porous carbon derived from activated biochar as a high-performance adsorbent for copper removal. *Sci Total Environ*, **692**: 844-853.
- Cuong D V, Wu P C, Liu N L, et al. 2020. Hierarchical porous carbon derived from activated biochar as an eco-friendly electrode for the electrosorption of inorganic ions. *Sep Purif Technol*, **242**: 116813.
- Cuong D V, Matsagar B M, Lee M S, et al. 2021. A critical review on biochar-based engineered hierarchical porous carbon for capacitive charge storage. *Renew Sustain Energy Rev*, **145**: 111029.
- de Souza L K C, Martins J C, Oliveira D P, et al. 2020. Hierarchical porous carbon derived from acai seed biowaste for supercapacitor electrode materials. *J Mater Sci Mater Electron*, **31**(15): 12148-12157.
- Dutta S, Bhaumik A, Wu K C. 2014. Hierarchically porous carbon derived from polymers and biomass: Effect of interconnected pores on energy applications. *Energy Environ Sci*, **7**(11): 3574-3592.
- Egun I L, He H Y, Hu D, et al. 2022. Molten salt carbonization and activation of biomass to functional biocarbon. *Adv Sustain Syst*, **6**(12): 2200294.
- Elmouwahidi A, Bailón-García E, Pérez-Cadenas A F, et al. 2020. Valorization of agricultural wood wastes as electrodes for electrochemical capacitors by chemical activation with H₃PO₄ and KOH. *Wood Sci Technol*, **54**(2): 401-420.
- Fang J Y, Shang Y S, Chen Z, et al. 2017. Rice husk-based hierarchically porous carbon and magnetic particles composites for highly efficient electromagnetic wave attenuation. *J Mater Chem C*, **5**(19): 4695-4705.
- FAO. 2018. FAO Rice Market Monitor (RMM), April 2018. <https://openknowledge.fao.org/handle/20.500.14283/i9243en>.
- Gao Y, Guo X B, Liu Y, et al. 2018. A full utilization of rice husk to evaluate phytochemical bioactivities and prepare cellulose nanocrystals. *Sci Rep*, **8**(1): 10482.
- Gunasekera U, Perera N, Perera S, et al. 2015. Modification of thermal conductivity of cotton fabric using Graphene. In: 2015 Moratuwa Engineering Research Conference (MERCon). April 7-8, 2015, Moratuwa, Sri Lanka: IEEE: 55-59.
- Hamouda H A, Cui S Z, Dai X W, et al. 2021. Synthesis of porous carbon material based on biomass derived from hibiscus sabdariffa fruits as active electrodes for high-performance symmetric supercapacitors. *RSC Adv*, **11**(1): 354-363.
- He H Z, Zhang R Q, Zhang P C, et al. 2023. Functional carbon from

- nature: Biomass-derived carbon materials and the recent progress of their applications. *Adv Sci*, **10**(16): e2205557.
- He S, Chen G Y, Xiao H, et al. 2021. Facile preparation of N-doped activated carbon produced from rice husk for CO₂ capture. *J Colloid Interface Sci*, **582**(Pt A): 90-101.
- Heidarinejad Z, Dehghani M H, Heidari M, et al. 2020. Methods for preparation and activation of activated carbon: A review. *Environ Chem Lett*, **18**(2): 393-415.
- Hou J Z, Mao X Y, Wang J Y, et al. 2021. Preparation of rice husk-derived porous hard carbon: A self-template method for biomass anode material used for high-performance lithium-ion battery. *Chem Phys*, **551**: 111352.
- Jalalah M, Han H, Nayak A K, et al. 2023a. Biomass-derived metal-free porous carbon electrocatalyst for efficient oxygen reduction reactions. *Journal of the Taiwan Institute of Chemical Engineers*, **147**: 104905.
- Jalalah M, Han H, Mahadani M, et al. 2023b. Novel interconnected hierarchical porous carbon derived from biomass for enhanced supercapacitor application. *J Electroanal Chem*, **935**: 117355.
- Jalalah M, Han H, Nayak A K, et al. 2024a. High-performance supercapacitor based on self-heteroatom-doped porous carbon electrodes fabricated from *Mikania micrantha*. *Adv Compos Hybrid Mater*, **7**(1): 20.
- Jalalah M, Nayak A K, Harraz F A. 2024b. Eco-friendly preparation of nitrogen-doped porous carbon materials for enhanced solid-state supercapacitor device. *Diam Relat Mater*, **147**: 111264.
- Jia C X, Chen J J, Liang J W, et al. 2020. Pyrolysis characteristics and kinetic analysis of rice husk. *J Therm Anal Calorim*, **139**(1): 577-587.
- Jiang G S, Senthil R A, Sun Y Z, et al. 2022. Recent progress on porous carbon and its derivatives from plants as advanced electrode materials for supercapacitors. *J Power Sources*, **520**: 230886.
- Junpen A, Pansuk J, Kamnoet O, et al. 2018. Emission of air pollutants from rice residue open burning in Thailand, 2018. *Atmosphere*, **9**(11): 449.
- Kaur P, Verma G, Sekhon S S. 2019. Biomass derived hierarchical porous carbon materials as oxygen reduction reaction electrocatalysts in fuel cells. *Prog Mater Sci*, **102**: 1-71.
- Kim J, Yi Y, Peck D H, et al. 2019. Controlling hierarchical porous structures of rice-husk-derived carbons for improved capacitive deionization performance. *Environ Sci: Nano*, **6**(3): 916-924.
- Kordi M, Farrokhi N, Pech-Canul M I, et al. 2024. Rice husk at a glance: From agro-industrial to modern applications. *Rice Sci*, **31**(1): 14-32.
- Larichev Y V, Yeletsky P M, Yakovlev V A. 2015. Study of silica templates in the rice husk and the carbon-silica nanocomposites produced from rice husk. *J Phys Chem Solids*, **87**: 58-63.
- Lesbayev B, Rakhymzhan N, Ustayeva G, et al. 2024. Preparation of nanoporous carbon from rice husk with improved textural characteristics for hydrogen sorption. *J Compos Sci*, **8**(2): 74.
- Li Y H, Mei J S, Wu L, et al. 2024. Ultrahigh surface area hierarchical porous carbon derived from biomass via a new KOH activation strategy for high-performance supercapacitor. *Int J Hydrog Energy*, **49**: 67-80.
- Liang X D, Liu R N, Wu X L. 2021. Biomass waste derived functionalized hierarchical porous carbon with high gravimetric and volumetric capacitances for supercapacitors. *Microporous Mesoporous Mater*, **310**: 110659.
- Liang Y R, Yang C, Dong H W, et al. 2017. Facile synthesis of highly porous carbon from rice husk. *ACS Sustainable Chem Eng*, **5**(8): 7111-7117.
- Liu D C, Zhang W L, Lin H B, et al. 2015. Hierarchical porous carbon based on the self-templating structure of rice husk for high-performance supercapacitors. *RSC Adv*, **5**(25): 19294-19300.
- Liu D C, Zhang W L, Huang W M. 2019. Effect of removing silica in rice husk for the preparation of activated carbon for supercapacitor applications. *Chin Chem Lett*, **30**(6): 1315-1319.
- Liu H, Liu R M, Xu C, et al. 2020. Oxygen-nitrogen-sulfur self-doping hierarchical porous carbon derived from *Lotus* leaves for high-performance supercapacitor electrodes. *J Power Sources*, **479**: 228799.
- Liu Y X, Tan H Y, Tan Z W, et al. 2023. Rice husk-derived carbon materials for aqueous Zn-ion hybrid supercapacitors. *Appl Surf Sci*, **608**: 155215.
- Liu Z Y, Sun Y, Xu X R, et al. 2020. Adsorption of Hg(II) in an aqueous solution by activated carbon prepared from rice husk using KOH activation. *ACS Omega*, **5**: 29231-29242.
- Lv S L, Li C X, Mi J G, et al. 2020. A functional activated carbon for efficient adsorption of phenol derived from pyrolysis of rice husk, KOH-activation and EDTA-4Na-modification. *Appl Surf Sci*, **510**: 145425.
- Mashhadimoslem H, Safarzadeh M, Ghaemi A, et al. 2021. Biomass derived hierarchical porous carbon for high-performance O₂/N₂ adsorption; a new green self-activation approach. *RSC Adv*, **11**(57): 36125-36142.
- Menya E, Olupot P W, Storz H, et al. 2018. Production and performance of activated carbon from rice husks for removal of natural organic matter from water: A review. *Chem Eng Res Des*, **129**: 271-296.
- Nandi R, Jha M K, Guchhait S K, et al. 2023. Impact of KOH activation on rice husk derived porous activated carbon for carbon capture at flue gas alike temperatures with high CO₂/N₂ selectivity. *ACS Omega*, **8**(5): 4802-4812.
- Nie W, Liu X L, Xiao Q M, et al. 2020. Hierarchical porous carbon anode materials derived from rice husks with high capacity and long cycling stability for sodium-ion batteries. *ChemElectroChem*, **7**(3): 631-641.
- Nizamuddin S, Siddiqui M T H, Baloch H A, et al. 2018. Upgradation of chemical, fuel, thermal, and structural properties of rice husk through microwave-assisted hydrothermal carbonization. *Environ Sci Pollut Res Int*, **25**(18): 17529-17539.
- Park B D, Wi S G, Lee K H, et al. 2003. Characterization of anatomical features and silica distribution in rice husk using microscopic and micro-analytical techniques. *Biomass Bioenergy*, **25**(3): 319-327.
- Peng L, Liang Y R, Huang J Y, et al. 2019. Mixed-biomass wastes derived hierarchically porous carbons for high-performance electrochemical energy storage. *ACS Sustainable Chem Eng*, **7**(12): 10393-10402.

- Premaratne W A P J, Priyadarshana W M G I, Gunawardena S H P, et al. 2014. Synthesis of nanosilica from paddy husk ash and their surface functionalization. *J Sci Univ Kelaniya*, **8**: 33-48.
- Qin Z Q, Ye Y Y, Zhang D, et al. 2023. One/two-step contribution to prepare hierarchical porous carbon derived from rice husk for supercapacitor electrode materials. *ACS Omega*, **8**(5): 5088-5096.
- Romero C, Liu Z, Wei Z, et al. 2024. A review of hierarchical porous carbon derived from various 3D printing techniques. *Nanoscale*, **16**(26): 12274-12286.
- Rybarczyk M K, Peng H J, Tang C, et al. 2016. Porous carbon derived from rice husks as sustainable bioresources: Insights into the role of micro-/ mesoporous hierarchy in hosting active species for lithium-sulphur batteries. *Green Chem*, **18**(19): 5169-5179.
- Saad M J, Hua C C, Misran S, et al. 2020. Rice husk activated carbon with NaOH activation: Physical and chemical properties. *Sains Malays*, **49**(9): 2261-2267.
- Sanni S O, Viljoen E L, Ofomaja A E. 2020. Three-dimensional hierarchical porous carbon structure derived from pinecone as a potential catalyst support in catalytic remediation of antibiotics. *RSC Adv*, **10**(15): 8717-8728.
- Sevilla M, Díez N, Fuertes A B. 2021. More sustainable chemical activation strategies for the production of porous carbons. *ChemSusChem*, **14**(1): 94-117.
- Shen Y F, Zhang N Y, Fu Y H. 2019. Synthesis of high-performance hierarchically porous carbons from rice husk for sorption of phenol in the gas phase. *J Environ Manage*, **241**: 53-58.
- Silva A P, Argondizo A, Juchen P T, et al. 2021. Ultrafast capacitive deionization using rice husk activated carbon electrodes. *Sep Purif Technol*, **271**: 118872.
- Siriwardane I W, Rathuwadu N P W, Dahanayake D, et al. 2021. Nano-manganese oxide and reduced graphene oxide-incorporated polyacrylonitrile fiber mats as an electrode material for capacitive deionization (CDI) technology. *Nanoscale Adv*, **3**(9): 2585-2597.
- Sun M H, Huang S Z, Chen L H, et al. 2016. Applications of hierarchically structured porous materials from energy storage and conversion, catalysis, photocatalysis, adsorption, separation, and sensing to biomedicine. *Chem Soc Rev*, **45**(12): 3479-3563.
- Sun N, Li Z Y, Zhang X, et al. 2019. Hierarchical porous carbon materials derived from kelp for superior capacitive applications. *ACS Sustainable Chem Eng*, **7**(9): 8735-8743.
- Tabata S, Iida H, Horie T, et al. 2010. Hierarchical porous carbon from cell assemblies of rice husk for *in vivo* applications. *Med Chem Commun*, **1**(2): 136-138.
- Tan Z X, Yang J W, Liang Y R, et al. 2021. The changing structure by component: Biomass-based porous carbon for high-performance supercapacitors. *J Colloid Interface Sci*, **585**: 778-786.
- Tian Y X, Xiao C Y, Yin D J, et al. 2019. Hierarchical porous carbon prepared through sustainable CuCl₂ activation of rice husk for high-performance supercapacitors. *ChemistrySelect*, **4**(8): 2314-2319.
- Wang C, Wang D Y, Zheng S, et al. 2018. Facile self-templating melting route preparation of biomass-derived hierarchical porous carbon for advanced supercapacitors. *Chem Res Chin Univ*, **34**(6): 983-988.
- Wang G Q, Wang D L, Kuang S, et al. 2014. Hierarchical porous carbon derived from rice husk as a low-cost counter electrode of dye-sensitized solar cells. *Renew Energy*, **63**: 708-714.
- Wang H, Shan L, Lv Q Y, et al. 2020. Production of hierarchically porous carbon from natural biomass waste for efficient organic contaminants adsorption. *J Clean Prod*, **263**: 121352.
- Wang Z F, Smith A T, Wang W X, et al. 2018. Versatile nanostructures from rice husk biomass for energy applications. *Angew Chem Int Edit*, **57**(42): 13722-13734.
- Wazir A H, Wazir I U, Wazir A M. 2024. Preparation and characterization of rice husk based physical activated carbon. *Energy Sources Part A Recovery Util Environ Eff*, **46**(1): 4875-4885.
- Xiang Y Y, Lu L Q, Kottapalli A G P, et al. 2022. Status and perspectives of hierarchical porous carbon materials in terms of high-performance lithium-sulfur batteries. *Carbon Energy*, **4**(3): 346-398.
- Xiao Y, Zheng M T, Chen X, et al. 2017. Hierarchical porous carbons derived from rice husk for supercapacitors with high activity and high capacitance retention capability. *Chemistry Select*, **2**(22): 6438-6445.
- Xue B C, Jin L, Chen Z M, et al. 2019. The template effect of silica in rice husk for efficient synthesis of the activated carbon based electrode material. *J Alloys Compd*, **789**: 777-784.
- Xue B C, Wang X F, Feng Y, et al. 2020. Self-template synthesis of nitrogen-doped porous carbon derived from rice husks for the fabrication of high volumetric performance supercapacitors. *J Energy Storage*, **30**: 101405.
- Yamaji N, Ma J F. 2009. A transporter at the node responsible for intervascular transfer of silicon in rice. *Plant Cell*, **21**(9): 2878-2883.
- Yan B, Zheng J J, Feng L, et al. 2023. Pore engineering: Structure-capacitance correlations for biomass-derived porous carbon materials. *Mater Des*, **229**: 111904.
- Yerdauletov M S, Nazarov K, Mukhametuly B, et al. 2023. Characterization of activated carbon from rice husk for enhanced energy storage devices. *Molecules*, **28**(15): 5818.
- Yin J, Zhang W L, Alhebshi N A, et al. 2020. Synthesis strategies of porous carbon for supercapacitor applications. *Small Meth*, **4**(3): 1900853.
- Yuan C J, Lin H B, Lu H Y, et al. 2016. Synthesis of hierarchically porous MnO₂/rice husks derived carbon composite as high-performance electrode material for supercapacitors. *Appl Energy*, **178**: 260-268.
- Zhang M X, Igalavithana A D, Xu L H, et al. 2021. Engineered/designer hierarchical porous carbon materials for organic pollutant removal from water and wastewater: A critical review. *Crit Rev Environ Sci Technol*, **51**(20): 2295-2328.
- Zhang S P, Zhang Q, Zhu S G, et al. 2021. Porous carbons derived from desilication treatment and mixed alkali activation of rice husk char for supercapacitors. *Energy Sources Part A Recovery Util Environ Eff*, **43**(3): 282-290.
- Zhao C J, Huang Y X, Zhao C H, et al. 2018. Rose-derived 3D carbon nanosheets for high cyclability and extended voltage supercapacitors. *Electrochim Acta*, **291**: 287-296.

- Zhao Y T, Mu J C, Wang Y Y, et al. 2023. Preparation of hierarchical porous carbon through one-step KOH activation of coconut shell biomass for high-performance supercapacitor. *J Mater Sci Mater Electron*, **34**(6): 527.
- Zhou X L, Zhang H, Shao L M, et al. 2021. Preparation and application of hierarchical porous carbon materials from waste and biomass: A review. *Waste Biomass Valorization*, **12**(4): 1699-1724.
- Zou X F, Dong C, Jin Y C, et al. 2023. Engineering of N, P Co-doped hierarchical porous carbon from sugarcane bagasse for high-performance supercapacitors and sodium ion batteries. *Colloids Surf A Physicochem Eng Aspects*, **672**: 131715.
- Zou Y P, Yang T K. 2019. Rice husk, rice husk ash and their applications. *Rice Bran and Rice Bran Oil*. Amsterdam: Elsevier: 207-246.

(Managing Editor: WU Yawen)

Journal Pre-proof